

TUTORIAL ON AC Resistance Calculation for Bare Stranded Conductors (TB345)

Prepared by Study Committee B2
Advisory Group 4 – Electrical Effects
January, 2009

- Calculation of AC Resistance of Stranded Conductor
 - DC Resistance
 - Temperature Effects
 - Skin Effect
 - Core Losses (ACSR)
 - “Transformer” Effect (ACSR)



Bare Conductor Resistance Overview

- Aluminum Strands carry 98% of current so Rdc primarily depends on aluminum conductivity and cross-section area.
- Helical stranding 2% increase in Rdc
- RDC increases 4% per 10C
- Skin Effect increase is 1% to 10%
- For ACSR, Transformer effect is <20% for 1-layer and <5% (multi-layer) for >2 amps/kcmil


DC Resistance

$$R_{dc} = 4 \rho_{20} [1 + \alpha_{20} (T - 20)] / \pi D_s^2$$


$$\frac{1}{R_{dc}} = \frac{\pi d_s^2}{4 \rho_s} \left(1 + \sum_1^{n_s} \frac{6 n_s}{k_{ns}} \right) + \frac{\pi d_a^2}{4 \rho_a} \left(1 + \sum_{n_a+1}^{n_a} \frac{6 n_a}{k_{na}} \right)$$

$$k_n = \left[1 + \left(\frac{\pi D_n}{\lambda_n} \right)^2 \right]^{1/2}$$


Transformer Effect

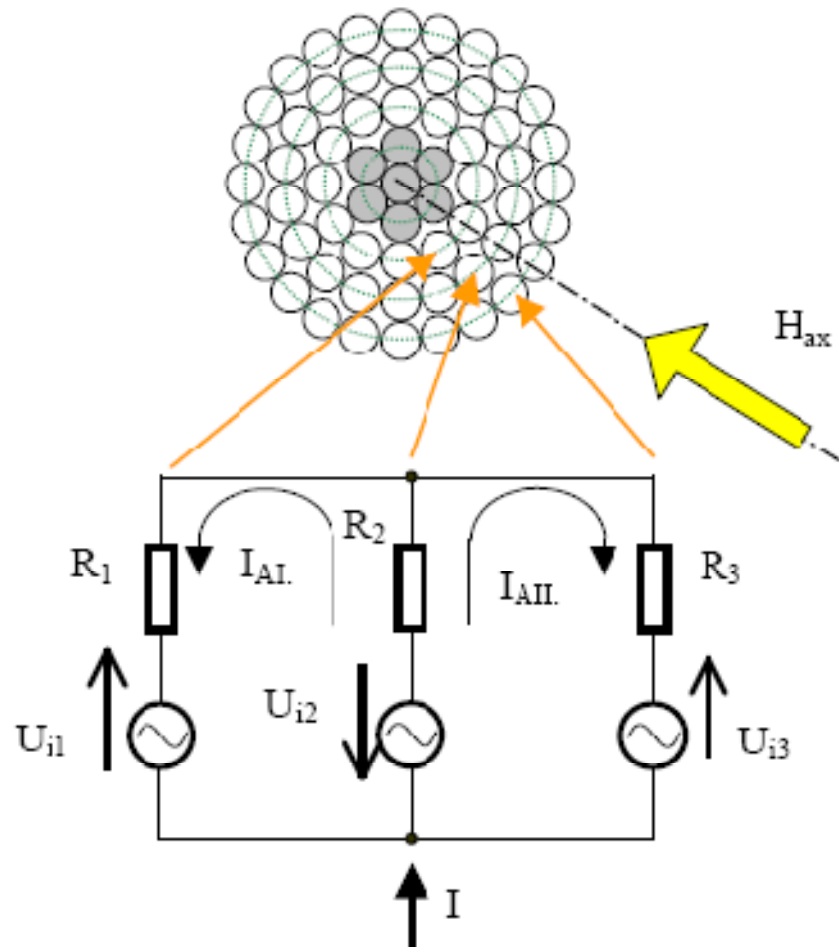

INCREASE IN RAC for Current

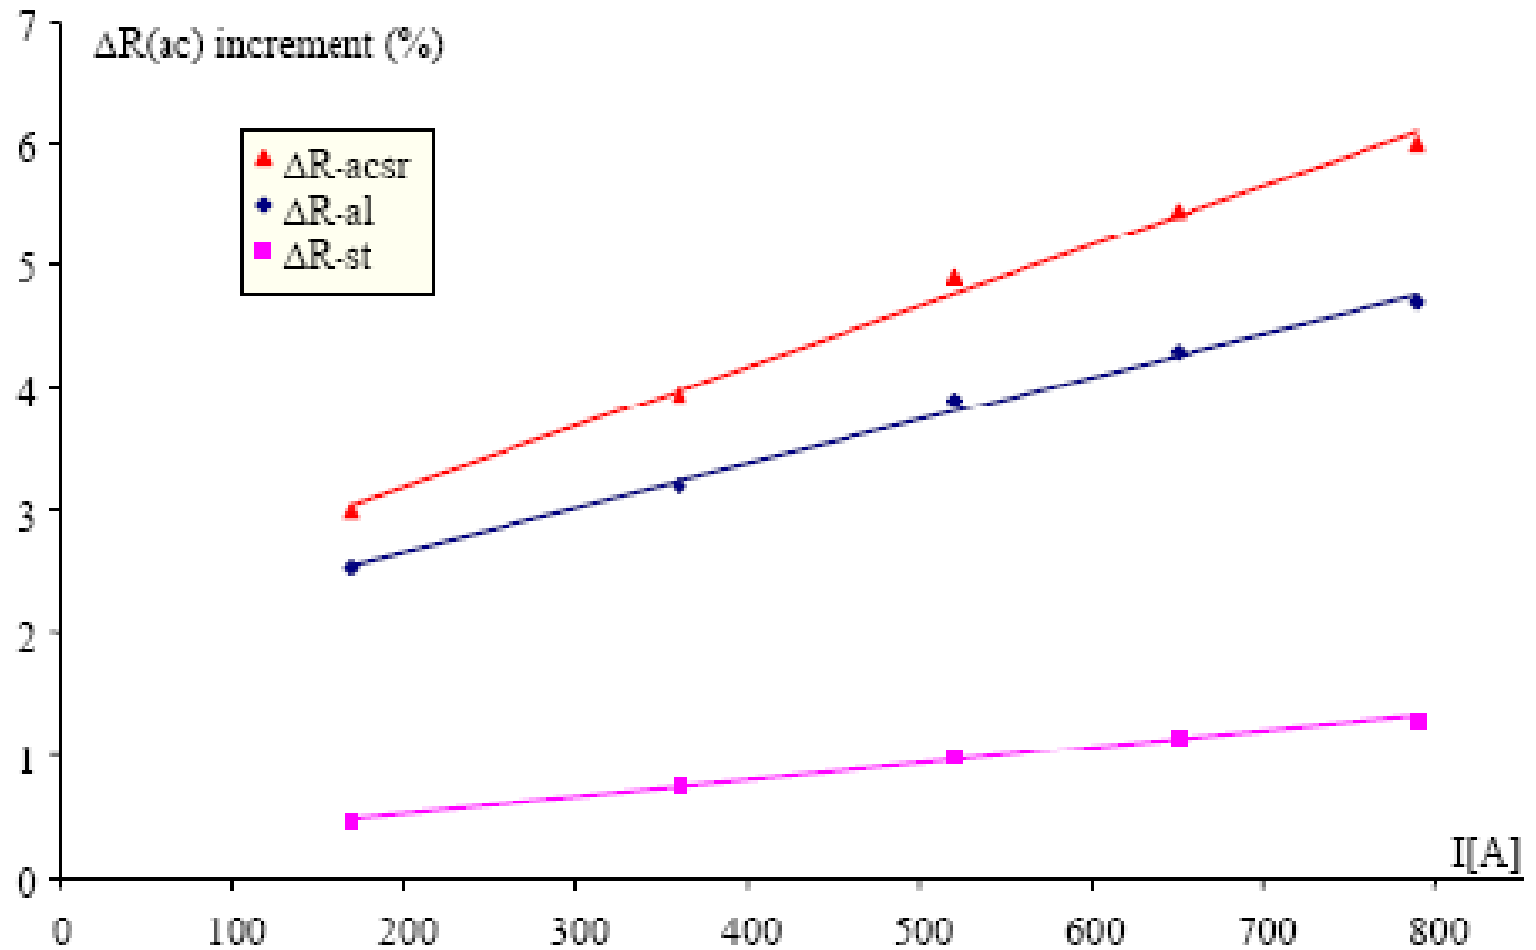


2-Layer ACSR

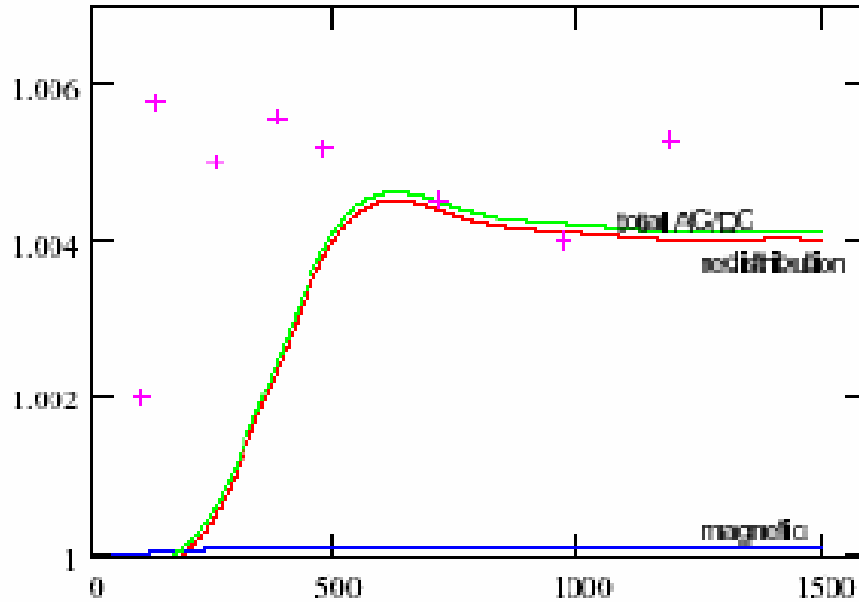

Notice that the core losses and transformer effect (magnetic coupling) is small for 2-layers of aluminum strands

Current (A)	Skin effect contribution	Current redistribution increment	Magnetic losses increment	Total AC/DC resistance ratio
0	0.000	0.000	0.000	1.000
250	0.004	0.0005	0.0001	1.0006
500	0.004	0.004	0.0001	1.0041
750	0.004	0.0043	0.0001	1.0044
1000	0.004	0.0041	0.0001	1.0042
1250	0.004	0.004	0.0001	1.0041
1500	0.004	0.004	0.0001	1.0041

3-Layer ACSR

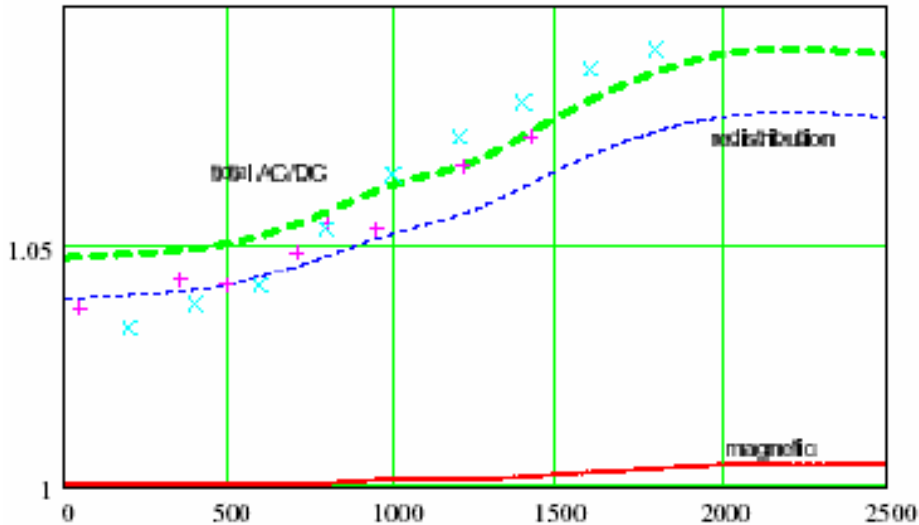

Notice that the core losses and transformer effect (magnetic coupling) is stronger for 3-layers of aluminum strands

Current (A)	Skin effect contribution	Current redistribution increment	Magnetic losses increment	Total AC/DC resistance ratio
0	0.000	0.000	0.000	1.000
250	0.008	0.040	0.001	1.049
500	0.008	0.042	0.001	1.051
750	0.008	0.047	0.001	1.056
1000	0.008	0.053	0.002	1.063
1250	0.008	0.058	0.002	1.068
1500	0.008	0.066	0.003	1.077
1750	0.008	0.073	0.004	1.085
2000	0.008	0.077	0.005	1.090
2250	0.008	0.078	0.005	1.091
2500	0.008	0.077	0.005	1.090

PROGRAM FOR CALCULATION OF AC RESISTANCE OF HELICALLY STRANDED CONDUCTORS


GENERAL INPUT DATA:

$f := 50$	Hz	- frequency		
$\mu_0 := 4 \cdot \pi \cdot 10^{-7}$	[7]	- magnetic permeability of the air		
$\rho_{st} := 0.1775$	$\frac{\Omega \cdot \text{mm}^2}{\text{m}}$	- specific resistance of steel, Code 1		
$\alpha_{st} := 0.00393$	$\frac{1}{\text{degC}}$	- temperature coefficient of steel	$\rho_{st} := 7.78$	$\frac{\text{kg}}{\text{dm}^3}$ - density of steel
$\rho_{al} := 0.0327$	$\frac{\Omega \cdot \text{mm}^2}{\text{m}}$	- specific resistance of alloy, Code 2		
$\alpha_{al} := 0.00360$	$\frac{1}{\text{degC}}$	- temperature coefficient of alloy	$\rho_{al} := 2.7$	$\frac{\text{kg}}{\text{dm}^3}$ - density of alloy
$\rho_{al} := 0.028126$	$\frac{\Omega \cdot \text{mm}^2}{\text{m}}$	- specific resistance of aluminium, Code 3		
$\alpha_{al} := 0.00404$	$\frac{1}{\text{degC}}$	- temperature coefficient of aluminium	$\rho_{al} := 2.7$	$\frac{\text{kg}}{\text{dm}^3}$ - density of aluminium

CONDUCTOR GEOMETRY DATA:

example: Grackle ACSR

$N_{st} := 3$		- number of steel layers
$N_{al} := 0$		- number of alloy layers
$N_{al} := 3$		- number of aluminium layers
$N = N_{st} + N_{al} + N_{al}$	$N = 6$	- total number of layers (limited to 7)
$M_0 := 1$		- material code of 1st layer (first wire in centre assumed as 1st layer)
$nW_0 := 1$	$dW_0 = 2.24$	- number and diameter (mm) of wires in 1st layer
$LayRatio_0 := 0$		- lay ratio of 1st layer

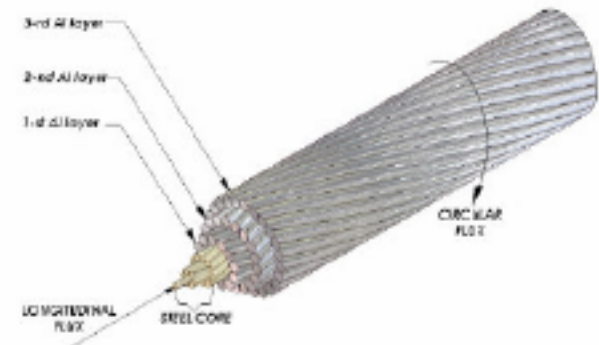

Conclusions

- Aluminum Strands carry 98% of current so Rdc primarily depends on aluminum conductivity and crossection area.
- Helical stranding 2% increase in Rdc
- RDC increases 4% per 10C
- Skin Effect increase is 1% to 10%
- For ACSR, Transformer effect is <20% for 1-layer and <5% (multi-layer) for >2 amps/kcmil